



# KEVLAR® engineered elastomer with Acrylonitrile Butadiene Rubber (NBR)

**Merge 1F770  
(Seal Formulation)**

## TEST COMPOUND FORMULATION

Nitrile Rubber	Krynac 34N50	100	90.8	84.6	69.2
1F770		0	12	20	40
N772 carbon black		60	60	60	60
Ether ester plasticizer	Thiokol TP 759	7	7	7	7
Mixed DPPD	Wingstay 100	2	2	2	2
Epoxy oil	Paraplex G 50	5	5	5	5
Stearic acid		0.5	0.5	0.5	0.5
Zinc oxide		4	4	4	4
MBT		2	2	2	2
MBTS		2	2	2	2
TETD		2	2	2	2
Sulfasan R		2	2	2	2
Engineered elastomer content (pphr)		0	12	20	40
Aramid Content (pphr)		0.0	2.8	4.6	9.2

## PROPERTIES

### Mooney Viscosity @ 100°C

ML 1+4	MU	40.0	44.2	46.0	54.2
--------	----	------	------	------	------

### Mooney Scorch MS 121°C

Time to +5	Mins	11.8	11.6	11.5	11.1
Time to +10	Mins	14.8	14.6	14.5	14.3
Minimum	MU	14.9	16.9	17.9	21.5

### Mooney Scorch MS 121°C aged 2 weeks @ 38C 100% RH

Time to +5	Mins	9.7	10.2	9.9	9.5
Time to +10	Mins	12.2	12.5	12.3	16.9
Minimum	MU	18.7	20.4	21.9	27.5

### Mooney Scorch MS 121°C aged 2 weeks @ 38C 100% RH & 2 weeks @ RT

Time to +5	Mins	12.0	11.9	12.1	11.0
Time to +10	Mins	15.1	14.9	15.7	14.4
Minimum	MU	23.6	24.1	27.5	34.5

### Mooney Scorch MS 121°C aged 2 weeks @ 38C 100% RH & 2 weeks @ RT & 2 weeks 100% RH

Time to +5	Mins	10.5	9.9	9.9	9.1
Time to +10	Mins	12.8	12.4	12.3	10.9
Minimum	MU	33.3	36.9	40.7	52.7

Engineered elastomer content (pphr)	0	12	20	40
Aramid Content (pphr)	0.0	2.8	4.6	9.2

### ODR 160°C 100 Range 30 mins

M <sub>L</sub>	DNm	6.31	7.58	8.59	10.22
T <sub>S2</sub>	Mins	1.71	1.63	1.63	1.63
T <sub>90</sub>	Mins	5.81	5.35	5.31	5.42
M <sub>H</sub>	DNm	82	87	92	102

### Vulcanisate Properties Measured on 2mm sheet cured 10 mins @160°C

#### Machine Direction

Hardness	° Shore A	58.8	71.3	74.8	83.2
Tensile Strength	MPa	16.3	14.4	12.2	13.2
Modulus @25%	MPa	0.8	2.3	4.2	12.9
Modulus @50%	MPa	1.3	5.1	8.1	14.3
Modulus @100%	MPa	2.2	6.6	8.9	
E/B	%	512	491	374	56
Density		1.201	1.205	1.21	1.216
DIN Abrasion	Cu mm	175	150	146	146
Tear, Die C	KNm	50.9	64.6	67.2	74.0

#### Cross Machine Direction

Tensile Strength	MPa	15.4	14	12.1	9.9
Modulus @25%	MPa	0.8	1.5	2.4	4.6
Modulus @50%	MPa	1.2	2.5	3.7	4.6
Modulus @100%	MPa	2.0	4.0	5.5	8.5
E/B	%	507	487	389	172

### Vulcanisate Properties Measured @ 100°C

Tensile Strength	MPa	5	6.1	6	7.9
Modulus @25%	MPa	0.7	1.8	4.5	7.8
Modulus @50%	MPa	1.2	3.6	5.9	
Modulus @100%	MPa	2.2	4.2	5.9	
E/B	%	189	217	141	35
Tear, Die C	KNm	13	21.2	27.8	41.7

### Air Aged 168 Hrs @ 100°C

Hardness	° Shore A	65.2	75.6	80.1	85.0
Change	%	6.4	4.3	5.2	1.8
Tensile Strength	MPa	17.7	15.5	13.5	16.9
Change	%	9	8	11	28
Modulus @ 50%	MPa	1.7	5.7	7.9	
Change	%	31	12	2	
E/B	%	427	388	277	40
Change	%	-17	-21	-26	-29

### Air Aged 72 Hrs @ 100°C in ASTM 1 Oil


Hardness	° Shore A	62.2	73.4	76.8	83.4
Change	° Shore A	3.4	2.1	2.0	0.2
Volume Change	%	-5.53	-5.65	-5.76	-6.22
Weight Change	%	-5.32	-5.46	-5.55	-5.92

### Air Aged 72 Hrs @ 100°C in ASTM 2 Oil


Hardness	° Shore A	58.1	69.7	75.9	85.0
Change	° Shore A	0.7	1.6	1.1	1.8
Volume Change	%	-0.05	-0.34	-0.55	-0.84
Weight Change	%	-0.83	-1.05	-1.25	-1.77

Engineered elastomer content (pphr)		0	12	20	40
Aramid Content (pphr)		0.0	2.8	4.6	9.2
<b>Air Aged 72 Hrs @ 100°C in ASTM 3 Oil</b>					
Hardness	° Shore A	55	70.2	75.7	83.6
Change	° Shore A	3.8	1.1	1.1	0.4
Volume Change	%	7.82	7.26	6.74	5.76
Weight Change	%	5.22	4.74	4.22	3.48
<b>Brittleness - ASTM 2137</b>					
	°C	-30	-26	-21	-17
<b>Low Temperature Torsional Stiffness - ISO 1432</b>					
T <sup>10</sup>	°C	-24.6	-24.6	-24.8	-24.6
T <sup>100</sup>	°C	-27.5	-29.4	-30.0	-30.7


**Modulus at 25% Elongation Machine Direction**

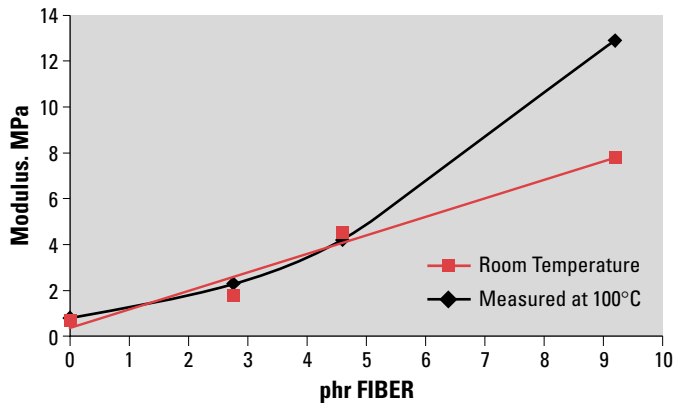


**Tear Strength, Die C**

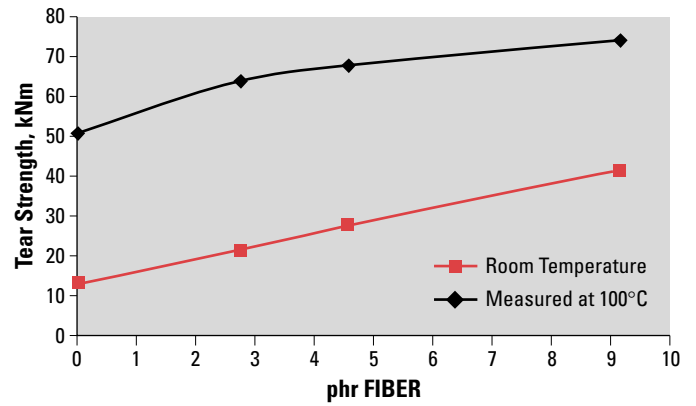

**DIN Abrasion**

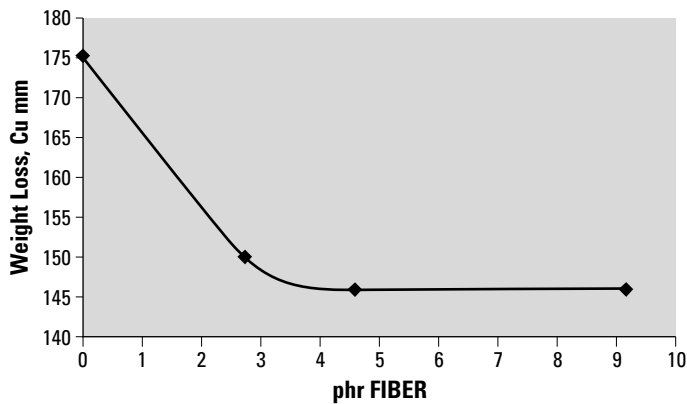

**Hardness Change**

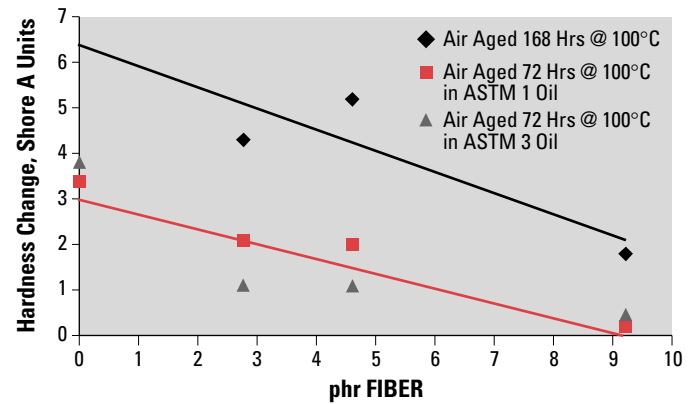

- Engineered elastomer merge 1F770 contains:
  - 23 weight percent reinforcement
  - 77 weight percent of a medium ACN content NBR rubber
- Specific gravity is 1.05
- ‘Nugget’ shape product form
- Packaged in 15 kilograms kraft bags with a low melt (<100°C) EVA liner

## S

### **United States and South America:**

DuPont Advanced Fibers Systems  
Customer Inquiry Center  
5401 Jefferson Davis Highway  
Richmond, VA 23234  
Tel: (800) 453-8527  
(804) 383-4400  
Fax: (800) 787-7086  
(804) 383-4132  
E-Mail: afscdt@usa.dupont.com  
Web Address: www.kevlar.com  
"

### **Canada:**

DuPont Canada Inc.  
Advanced Fibers Systems  
P.O. Box 2200  
Streetsville Postal Station  
Mississauga, Ontario L5M 2H3  
Tel: (905) 821-5193  
Fax: (905) 821-5177

### **Europe:**

DuPont Engineering Fibres  
P.O. Box 50  
CH-1218 Le Grand-Saconnex  
Geneva, Switzerland  
Tel. ++ 41-22-717 51 11  
Fax: ++ 41-22-717 60 21

### **Asia:**

DuPont (Thailand) Limited  
9-11th Floor, Yada Building  
56 Silom Road  
Suriyawongse, Bangrak  
Bangkok 10500 Thailand  
Tel: 662-2360026, 662-2384361 Ext 2702  
Fax: 662-2367300

### **Japan:**

DuPont Toray Company, Inc.  
1-5-6 Nihombashi-Honcho,  
Chuo-ku, Tokyo 103  
Japan  
Tel: 81-3-3245-5080  
Fax: 81-3-3242-3183

KEVLAR® is a registered trademark of E. I. du Pont de Nemours and Company

---

This information represents our current knowledge on the subject. It is offered solely to provide possible suggestions for your own experimentation. It is not intended, however, to substitute for any testing you may need to conduct to determine for yourself the suitability of our products for your particular purposes. This information is subject to revision as new knowledge and experience becomes available. Since we cannot anticipate all variations in actual end-use conditions, DuPont makes no warranties and assumes no liability in connection with any use of this information. Nothing in this publication is to be considered as a license to operate under or a recommendation to infringe any patent right.

